

Effect of Coconut Shell as A Coarse Aggregates on Behaviour of Concrete

SHUBHANGI B. DHOBLE¹, DR. S. G. MAKARANDE², PROF. V. A. KALMEGH³

¹ PG Student, Bapurao Deshmukh College of Engineering, Sevagram, Wardha

^{2,3} Professor, Bapurao Deshmukh College of Engineering, Sevagram, `Wardha

Abstract- Nature resources such as river sand and coarse aggregate are depleting at an alarming level in developing countries like India from study. The high demand for concrete in the construction using normal weight aggregates such as gravel and granite drastically reduces the natural stone deposits and this has damaged the environment thereby causing ecological imbalance. Therefore, there is a need to explore and to find out suitable replacement material to substitute the natural stone. In developed countries, the construction industries have identified many artificial and natural lightweight aggregates (LWA) that have replaced conventional aggregates thereby reducing the size of structural members. This has brought immense change in the development of high-rise structures using LWC. The coconut shell was used as a Replacement of coarse aggregate. The quantity of coconut shell is 0%, 5%, 10%, 15% replacement by coarse aggregate and cubes were casted and crushed in order to investigate the compressive strength. use of coconut shell as a substitute of aggregate will be not only is cost effective and eco-friendly, but also help to resolve the problem of disposal of shortage of conventional material such as coarse aggregate.

Indexed Terms- Coconut shell, aggregate, partial replacement, lightweight concrete, Coconut Shell, Coarse Aggregate

I. INTRODUCTION

Concrete is an artificial material similar to similar in appearance & properties to some natural lime stone rock .The major component of concrete is natural aggregate such as gravel or crushed rock ,sand and fine particles of cement powder and ultimately mixed with water .while the construction material cost is increasing day by day ;the reasons are high demand ,scarcity of raw material as well as high price of energy

.Coconut shell represents more than 60% of domestic waste volume .coconut shell is an abundantly available agricultural waste from local industries .So, in developing countries like India, these can be used as potential material or replacement material in the construction field. This will ultimately lead to the reduction in the cost of construction material as well as means of disposal of waste. Infrastructure development across the world created demands for construction material. Concrete is the premier civil engineering materials used in the structure. Concrete manufacturing involves consumption of ingredients like cement, aggregates, water and admixtures. Among all the ingredients, aggregates form the major parts. Production is expected to increase to more than billions of tons per year by the year. Use of natural aggregates in such a rate leads to a question about the preservation of natural aggregate sources. Using alternative materials in place of natural aggregates in concrete production makes concrete as sustainable and environmentally friendly construction material. The chemical composition of coconut shell is similar to wood and it contains 33.61% cellulose, 36.51 % lignin and 0.61% ash.

II. AIM & OBJECTIVE

Aim: To encourage the use of these harm free waste products as construction materials in low-cost housing. Analyzing flexural and compressive strength characteristics of concrete produced using crushed, granular coconut as substitutes for conventional coarse aggregate.

Objective:

- To encourage the use of these ‘seemingly’ waste products as construction materials in low-cost housing.

- It is also expected to serve the purpose of encouraging housing developers in investing these materials in house construction.

III. LITERATURE VIEW

Siti Aminah Bt Tukiman and Sabarudin Bin Mohd (2009): replaced the coarse aggregate by coconut shell and grained palm kernel in their study. Percentage of replacement by coconut shell were 0%, 25%, 50%, 75% and 100% respectively. Conclusion is that the combination of these materials has potential of being used as lightweight aggregate in concrete and also has reduce the material cost in construction

Olutoge (2010) studied the saw dust and palm kernel shells (PKS). Fine aggregates are replaced by saw dust and coarse aggregates by palm kernel shells in reinforced concrete slabs casting. Conventional aggregates were replaced by saw dust and PKS in same ratios of 0%, 25%, 50%,75% and 100%. Compressive and flexural strengths were noted at different time intervals. It was seen that at 25% sawdust and PKS can produce lightweight reinforced concrete slabs that can be used where low stress is required at reduced cost. 7.43% reduction can be achieved

J. P. Ries (2011) observed that Lightweight aggregate plays important role in today’s move towards sustainable concrete. Lightweight aggregates contribute to sustainable development by lowering transportation requirements, optimizing structural efficiency that results in a reduction in the amount of overall building material being used, conserving energy, reducing labour demand and increasing the life of structural concrete

Maninder Kaur & Manpreet Kaur (2012) published a review paper in which it is concluded that use of coconut shells in cement concrete can help in waste reduction and pollution reduction. It is also expected to serve the purpose of encouraging housing developers in investing these materials in house construction. It is also concluded that the Coconut Shells are more suitable as low strength giving lightweight aggregate when used to replace common coarse aggregate in concrete production

Vishwas P. Kulkarni et al (2013) studied that Aggregates provide volume at low cost, comprising 66 percent to 78 percent of the concrete. M20 Concrete is produced by 0%, 10%, 20%, 30% replacement of coarse aggregate by coconut shell. There is no need to treat the coconut shell before use as an aggregate except for water absorption. No bond failure was observed, confirming that there was adequate bonding between the coconut shell aggregate concrete and the steel bars

IV. COCONUTSHELL AGGREGATE

Crush coconut shell as coarse aggregates and this coconut shell aggregate was used as partial replacement of coarse aggregate. which is crushed stone coconut shell were unruffled from the local seller after that it was clean, sun dry remove fibres to evaluate its properties. Coconut shell needs no pre-treatment, for water absorption. Due to the property, before use coconut shell were in portable water for 24 hours

V. MIX DESIGN

5.1 Definition

Mix design is the process of selecting suitable ingredient if concrete and determines their relative proportions with the object of certain minimum strength and durability as economically as possible.

5.2 Objective of Mix Design

The objective of concrete mix design as follows.

- The first objective is to achieve the stipulated minimum strength.
- The second objective is to make the concrete in the most economical Manner. Cost wise all concrete’s depend primarily on two factors, namely cost of material and cost of labor.

5.3 Mix Proportion

Cement	Fine aggregate	Coarse aggregate	Water
288	790.02	994	170.39
1	2.21	3.09	0.45

VI. MATERIAL PROPERTIES

6.1 Cement:

Ordinary Portland cement of 43 grade conforming to Indian Standard IS 12269-1987 9 was used throughout the experimental program. The standard consistency was 28%, whereas the initial and final setting times were 95 min. and 210 min. respectively. The specific gravity of cement was 3.14 and its compressive strength after 28 days was 57 MPa.

6.2 Coarse Aggregate:

In this investigation, two types of coarse aggregates were used for preparation of concrete, Natural Coarse Aggregate. (NCA) and coconut shell Coarse Aggregate. (CSA)

6.3 Natural Coarse Aggregate (NCA)

Crushed hard granite chips of maximum size 20 mm were used in the concrete mixes. The bulk density of aggregate was 1460 kg/m³ and specific gravity was found to be 2.65.

6.4 Sand:

Fine aggregate (sand) used for this entire investigation for concrete was river sand conforming to zone-II of IS: 383-1970 10. The fineness modulus was 2.81.

6.5 Water:

Potable water conforming to IS 456-2000 11 was used for casting and curing

VII. PREPARATIO OF SPECIMENS

7.1 Batching:

All cement, sand, coarse aggregate and coconut shell measured with digital balance. Water is measuring cylinder of capacity 1 lit and measuring jar of capacity 100 ml and 200 ml.

7.2 Mixing of concrete:

The ingredients are thoroughly mixed in concrete mixer. The sand, cement and aggregate are measured accurately.

7.3 Moulds:

Concrete moulds are cubes (150 mm x 150 mm x 150 mm), cleaned first and oiled for easy stripping. The

moulds for conducting tests on fresh concrete were made ready and inner surface was oiled.

7.4 Placing and Compaction:

To avoid the bond formation between moulds and concrete just clean and oil the moulds before pouring concrete. Place the fresh concrete and tamp each surface 25 time. Clean the mounds and apply grease. Fill the concrete in the moulds in 3 equal layers.

7.5 Demoulding:

After leveling the fresh concrete in the mould, it was allowed to set for 24 hours. The identification marks of concrete specimens were done with permanent markers and the specimens were removed from the mould. The moulds were cleaned and kept ready for next batch of concrete mix.

7.6 Curing:

Curing is an important process to prevent the concrete specimens from losing their moisture while they are gaining their required strength. Inadequate curing is also the cause of unexpected cracks on the surface of concrete specimen

VIII. COMPRESSIVE TEST RESULT


%Replac ed by coconut shell	Da ys	Cub es	0 %	5%	10 %	15 %
Compres sive Strength (N/mm ²)	7 Da ys	C1	21.87	18.89	19.98	15.89
		C2	21.60	18.40	19.87	15.78
		C3	21.35	18.15	19.50	15.50
		Avg	21.60	18.48	19.78	15.72

Table No.1 Result of compressive Strength of coconut shell concrete after 7 days (N/mm²)

% Replaced by coconut shell	Da ys	Cub es	0%	5%	10 %	15 %

Compressive Strength (N/mm ²)	14 Days	C4	25.75	23.25	24.98	20.9
		C5	25.40	23.10	24.67	20.8
		C6	25.30	23.01	24.35	20.5
		Avg	25.48	23.12	24.66	20.7

Table No.2 Result of compressive Strength of coconut shell concrete after 14 days (N/mm²)

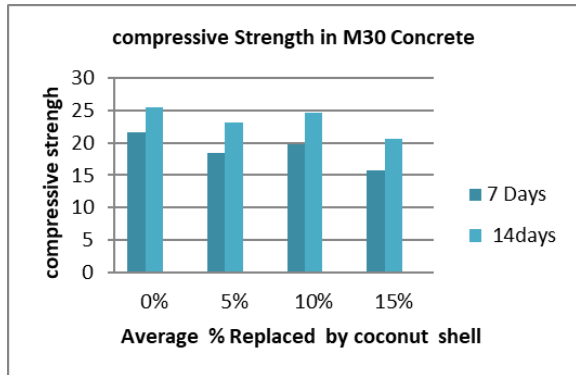

CONCLUSION

- Up to 10% of aggregate replaced by coconut shell is good according to strength and cost wise.
- increase in percentage replacement by coconut shell reduced the strength and density of concrete.
- It helps in reducing up to 15% pollution in environment.
- It is concluded that the coconut shell is more suitable as low strength giving lightweight aggregate when used to replace common coarse aggregate in concrete production.

FUTURE WORK

- This study can be extended by using coconut shell under different physical conditions such as tender coconut shell, dried coconut shell etc.
- Seismic analysis of structure made by concrete with partial replacement of coarse aggregate with coir fibres and coconut shell can be carried out.

APPLICATIONS

- It is used in low-cost building and marine structures
- Used as concrete blocks
- Eco friendly
- It is used as lightweight concrete for construction of footpath pavement

REFERENCES

- [1] Siti Aminah Bt Tukiman and Sabarudin Bin Mohd “Investigatio the combination of coconut shell and grained palm kernel to replace aggregate in concrete: A technical review National Conference on Postgraduate Research (NCONPGR) 2009, UMP Conference Hall, Malaysia.
- [2] Olutoge F.A,” Investigations on Sawdust and Palm Kerne lShells As Aggregate Replacement”, ARPN Journal of Engineering and Applied Sciences VOL.5. NO.4, April 2010.
- [3] Abdulfatah Abubakar and Muhammed Saleh Abubakar, Exploratory Study of Coconut Shell as Coarse Aggregate in Concrete, Journal of Engineering & Applied sciences, vol.3, December 2011.
- [4] Maninder Kaur & Manpreet Kaur, Review on Utilization of Coconut Shell as Coarse Aggregates in Mass Concrete, International Journal of Applied Engineering Research, vol.7, Issue 11, 2012.
- [5] Daniel Yaw Osei, Experimental assessment on coconut shells as aggregate in concrete, International Journal of Engineering Science Invention, vol. 2, Issue 5, May 2013
- [6] Parag S. Kambli and Sandhya R. Mathapati, Compressive Strength of Concrete by Using Coconut Shell, IOSR Journal of Engineering (IOSRJEN) www.iosrjen.org ISSN (e): 22503021, ISSN (p): 2278-8719 Vol. 04, Issue 04 (April. 2014)
- [7] Abdullahi M (2012), Effect of aggregate type on compressive strength of concrete, International journal of civil & structural engineering, vol 2,

no3, pp 791-800. M. Abdullahi, H. M. A. Al-Mattarneh, A. H. Abu Hasan, Md. H. Hassan & B. S. Mohammed (2008), Trial mix design methodology for palm oil clinker (POC), International conference on construction & building technology, pp 507-516.

- [8] U. J. Alengaram, M. Z. Jumaat & H. Mahmud (2008), Influence of cementitious materials & aggregate content on compressive strength of palm kernel shell concrete, Journal of applied science, Vol 8, issue18, ppt 3207-3213
- [9] U. Johnson Alengaram,. U. J. Alengaram, M. Z. Jumaat & H. Mahmud (2008), influence of sand content and silica fume on mechanical properties of palm kernel shell concrete, international conference on construction and building technology vol 23pp 251-26